

AD-A249 500



2

AD

TECHNICAL REPORT ARCCB-TR-92009

**NONLINEAR STRESS ANALYSIS OF
COMPOSITE-JACKETED STEEL CYLINDERS
SUBJECTED TO HIGH INTERNAL PRESSURE**

PETER C.T. CHEN

DTIC
SELECTE
APR 30 1992
S B D

MARCH 1992



**US ARMY ARMAMENT RESEARCH,
DEVELOPMENT AND ENGINEERING CENTER
CLOSE COMBAT ARMAMENTS CENTER
BENÉT LABORATORIES
WATERVLIET, N.Y. 12189-4050**



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

92 4 28 324

92-11743



DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

DESTRUCTION NOTICE

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19 or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE March 1992	3. REPORT TYPE AND DATES COVERED Final	
4. TITLE AND SUBTITLE NONLINEAR STRESS ANALYSIS OF COMPOSITE-JACKETED STEEL CYLINDERS SUBJECTED TO HIGH INTERNAL PRESSURE			5. FUNDING NUMBERS AMCMS No. 6111.02.H610.0 PRON No. 1A11Z1CANMBJ	
6. AUTHOR(S) Peter C.T. Chen				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Benet Laboratories, SMCAR-CCB-TL Watervliet, NY 12189-4050			8. PERFORMING ORGANIZATION REPORT NUMBER ARCCB-TR-92009	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES To be presented at the Pressure Vessels and Piping Conference, New Orleans, LA, 21-25 June 1992 Submitted for publication in the Proceedings of the Conference				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) This report presents a nonlinear stress analysis of a thick-walled compound tube subjected to high internal pressure. The compound tube is constructed of a steel liner and a graphite-bismaleimide outer shell. Analytical expressions for the stresses, strains, and displacements are derived for all loading ranges up to failure. Numerical results for the stresses and the maximum value that the compound tube can contain without failure are presented.				
14. SUBJECT TERMS Compound Tube, Composite Jacket, Steel Liner, Elastic-Plastic, Fully-Plastic, Failure Analysis			15. NUMBER OF PAGES 22	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

TABLE OF CONTENTS

	<u>Page</u>
ACKNOWLEDGEMENTS	iii
INTRODUCTION	1
PROBLEM AND ELASTIC ANALYSIS	1
ELASTIC-PLASTIC ANALYSIS	3
FULLY-PLASTIC ANALYSIS	5
FAILURE ANALYSIS	6
DISCUSSION OF RESULTS	6
CONCLUSION	8
REFERENCES	9

TABLES

1. ELASTIC CONSTANTS OF COMPOSITE JACKET AND STEEL LINER	2
--	---

LIST OF ILLUSTRATIONS

1. Schematic of a compound tube problem	10
2. Interface pressure as a function of internal pressure	10
3. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 1	11
4. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 2	12
5. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 3	13
6. Hoop stresses at the bore and interface as functions of internal pressure for case 1	14
7. Hoop stresses at the bore and interface as functions of internal pressure for case 2	15
8. Hoop stresses at the bore and interface as functions of internal pressure for case 3	16
9. Distribution of hoop stresses in the liner and jacket for case 1	17

	<u>Page</u>
10. Distribution of hoop stresses in the liner and jacket for case 2	18
11. Distribution of hoop stresses in the liner and jacket for case 3	19

ACKNOWLEDGEMENTS

The author wishes to thank K. Miner, M. Scavullo, and M. Witherell of Benet Laboratories for helpful discussions.

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/ _____	
Availability Codes	
Dist	Avail and/or Special
A-1	

INTRODUCTION

Weight reduction is a requirement for a majority of weapon systems being developed by the Army. The Army would like to design longer cannon and maintain the inertia characteristics of the shorter cannon. This accomplishment would allow current cannon mounts to be used. The longer cannon is expected to achieve higher muzzle velocity and greater accuracy than the standard cannon. The design under consideration is to replace a portion of the steel wall thickness with a lighter material. The inner portion, steel liner, maintains the tube projectile interface and shields the composite from the extremely hot gases. The outer portion, composite jacket, is made of a fiber-reinforced organic composite (graphite fiber and a bismaleimide matrix). A linear stress analysis for this problem under internal pressure in the elastic range was reported in a recent paper by M.D. Witherell and M.A. Scavullo (ref 1).

This report presents a nonlinear stress analysis of the compound tube problem. The loading ranges include elastic, elastic-plastic, and fully-plastic up to failure. Analytical expressions for the stresses, strains, and displacements are derived for all cases. Numerical results for the radial and hoop stresses in the nonlinear loading ranges are presented. The maximum value of internal pressure that the compound tube can contain without failure is predicted.

PROBLEM AND ELASTIC ANALYSIS

Figure 1 shows a schematic of the compound tube problem. The compound tube consists of an inner steel "liner" and an outer composite "jacket." The steel liner of inside radius a and outer radius b is wrapped in the circumferential direction with a graphite-bismaleimide organic composite of outside radius c .

The elastic material constants for the composite and the steel are given in Table 1.

TABLE 1. ELASTIC CONSTANTS OF COMPOSITE JACKET AND STEEL LINER

Elastic Constants for IM6/Bismaleimide, 55% F.V.R.		
$E_r = 1.126 \text{ Mpsi}$ (7.758 Gpa)	$\nu_{r\theta} = 0.01524$	$\nu_{\theta r} = 0.3155$
$E_\theta = 23.31 \text{ Mpsi}$ (160.61 Gpa)	$\nu_{\theta z} = 0.3155$	$\nu_{z\theta} = 0.01524$
$E_z = 1.126 \text{ Mpsi}$ (7.758 Gpa)	$\nu_{zr} = 0.3991$	$\nu_{rz} = 0.3911$
Elastic Constants for Steel		
$E = 30.0 \text{ Mpsi}$ (206.7 Gpa)	$\nu = 0.3$	

When the composite tube is subjected to internal pressure p in the elastic range, the general solutions in the plane-strain condition for the isotropic liner ($a \leq r \leq b$) are

$$\sigma_r \quad (1)$$

$$\sigma_\theta = \{ \mp(p-q) \left(\frac{b}{r}\right)^2 + p - q b^2/a^2 \} / \left(\frac{b^2}{a^2} - 1\right) \quad (2)$$

$$u/r = E^{-1}(1+\nu) [(p-q)(b/r)^2 + (1-2\nu)(p-q b^2/a^2)] / \left(\frac{b^2}{a^2} - 1\right) \quad (3)$$

and for the orthotropic jacket ($b \leq r \leq c$),

$$\sigma_r = q \left[- \left(\frac{c}{b}\right)^{k-1} \left(\frac{c}{r}\right)^{k+1} + \left(\frac{r}{b}\right)^{k-1} \right] / [(c/b)^{2k} - 1] \quad (4)$$

$$\sigma_\theta = kq [(c/b)^{k-1} \left(\frac{c}{r}\right)^{k+1} + \left(\frac{r}{b}\right)^{k-1}] / [(c/b)^{2k} - 1] \quad (5)$$

$$u/r = \epsilon_\theta = a_{12}\sigma_r + a_{22}\sigma_\theta \quad (6)$$

where q is the pressure at the interface, $k = (a_{11}/a_{22})^{1/2}$,

$$a_{11} = (1 - \nu_{rz}\nu_{zr})/E_r$$

$$a_{12} = - (\nu_{\theta r} + \nu_{\theta z}\nu_{zr})/E_\theta$$

$$a_{22} = (1 - \nu_{\theta z}\nu_{z\theta})/E_\theta \quad (7)$$

By requiring the displacement to be continuous at the interface, the interface pressure q can be expressed as a linear function of internal pressure p ,

$$\frac{2p}{q} = \left(\frac{b^2}{a^2} - 1\right) \left[Ak \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} + B \right] + \frac{b^2}{a^2} + 1 \quad (8)$$

where

$$A = E\alpha_{22}/(1-\nu^2), \quad B = -E\alpha_{12}/(1-\nu^2) - \nu/(1-\nu) \quad (9)$$

Now all the stresses, strains, and displacements in the tube ($a \leq r \leq c$) can be determined as functions of p . In particular, the expressions for the displacements at the bore (u_a), interface (u_b), and outside surface (u_c) are

$$\left(\frac{b^2}{a^2} - 1\right) \frac{E}{p} \frac{u_a}{a} = (1+\nu) \frac{b^2}{a^2} + (1-\nu-2\nu^2) - \frac{4(1-\nu^2)(b^2/a^2)}{\left(\frac{b^2}{a^2} - 1\right) \left[Ak \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} + B \right] + \frac{b^2}{a^2} + 1} \quad (10)$$

$$\frac{u_b}{b} = q \left[k\alpha_{22} \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} - \alpha_{12} \right] \quad (11)$$

$$\frac{u_c}{c} = \frac{2qk\alpha_{22}(c/b)^{k-1}}{(c/b)^{2k} - 1} \quad (12)$$

ELASTIC-PLASTIC ANALYSIS

When the internal pressure p is large enough, part of the steel liner will become plastic. Using Tresca's yield criterion, the associated flow rule, and assuming linear strain-hardening, the elastic-plastic solution based on Bland can be used (refs 2,3). Let ρ be the elastic-plastic interface.

The solution can be written in the elastic portion ($\rho \leq r \leq b$) as

$$\frac{E}{\sigma_0} \frac{u}{r} = \frac{1+\nu}{2} \frac{\rho^2}{r^2} + (1-\nu-2\nu^2) \left[\frac{1}{2} \frac{\rho^2}{b^2} - \frac{q}{\sigma_0} \right] \quad (13)$$

$$\sigma_r/\sigma_0 \quad (14)$$

$$= \frac{1}{2} \left(\frac{\rho^2}{r^2} + \frac{\rho^2}{b^2} \right) - \frac{q}{\sigma_0} \quad (15)$$

$$\sigma_z/\sigma_0 = \nu \rho^2/b^2 - 2\nu q/\sigma_0 \quad (16)$$

and in the plastic portion ($a \leq r \leq \rho$)

$$\frac{E}{\sigma_0} \frac{u}{r} = (1-\nu-2\nu^2) \frac{\sigma_r}{\sigma_0} + (1-\nu^2) \frac{\rho^2}{r^2} \quad (17)$$

$$\sigma_r/\sigma_0 \quad (18)$$

$$\sigma_\theta/\sigma_0 = \mp \frac{1}{2} (1-\eta\beta+\eta\beta \frac{\rho^2}{r^2}) + \frac{1}{2} \frac{\rho^2}{b^2} - (1-\eta\beta) \ln \frac{\rho}{r} - \frac{g_-}{\sigma_0} \quad (19)$$

$$\sigma_z/\sigma_0 = \nu \rho^2/b^2 - 2\nu(1-\eta\beta) \ln \frac{\rho}{r} - 2\nu q/\sigma_0 \quad (20)$$

$$\bar{\epsilon}^p = \beta(\rho^2/r^2-1) \quad , \quad \eta\beta = \frac{m}{m + \frac{3}{4} \frac{(1-m)}{(1-\nu)^2}} \quad (21)$$

$$\eta = \frac{2}{\sqrt{3}} \frac{E}{\sigma_0} \frac{m}{1-m} \quad , \quad m = \frac{E_t}{E} \quad , \quad \sigma = \sigma_0(1+\eta\epsilon^p) \quad (22)$$

where σ_0 is the initial tensile yield stress, and E_t is the tangent modulus in the plastic range of the stress-strain curve.

Using Eqs. (11) and (13) and the requirement of displacement continuity at the interface, i.e., u_{b-} (liner) = u_{b+} (jacket), we obtain the expression for the interface pressure q as

$$\frac{g_-}{\sigma_0} = \frac{(1-\nu^2)\rho^2/b^2}{(1+\nu)(1-2\nu) + E[\alpha_{22k} \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} - \alpha_{12}]} \quad (23)$$

Given any value of ρ in $a \leq \rho \leq b$, we can now determine q , u , and all the stresses and strains in the tube. In particular, the expressions for internal pressure and for displacements at the bore and the interface are

$$\frac{p_-}{\sigma_0} = \frac{g_-}{\sigma_0} + \frac{1}{2} (1 - \frac{\rho^2}{b^2}) + (1-\eta\beta) \ln \frac{\rho}{a} + \frac{1}{2} \eta\beta (\frac{\rho^2}{a^2} - 1) \quad (24)$$

$$\frac{E}{\sigma_0} \frac{u_a}{a} = - (1-\nu-2\nu^2) \frac{p_-}{\sigma_0} + (1-\nu^2) \rho^2/a^2 \quad (25)$$

$$\frac{E}{\sigma_0} \frac{u_b}{b} = (1-\nu^2) \frac{\rho^2}{b^2} - (1-\nu-2\nu^2) \frac{g_-}{\sigma_0} \quad (26)$$

By letting $p = a$ and b , we can determine the lower limits p^* , q^* , u_a^* , u_b^* , u_c^* , and the upper limits p^{**} , q^{**} , u_a^{**} , u_b^{**} , u_c^{**} , respectively.

FULLY-PLASTIC ANALYSIS

When the internal pressure p is further increased, i.e., $p > p^{**}$, the steel liner will become fully-plastic. The composite jacket remains elastic as long as the failure pressure is not reached. Using Tresca's yield criterion, the associated flow rule, and assuming linear strain-hardening, a fully-plastic solution can be obtained (ref 4). The result is presented here for completeness. The explicit expressions for the displacement, strains, and stresses in the plane-strain case, subject to $\sigma_\theta \geq \sigma_z \geq \sigma_r$, are

$$ru = E^{-1}(1-2\nu)(1+\nu)r^2\sigma_r + \phi b^2 \quad (27)$$

$$\sigma_r = -p + \sigma_0(1-\eta\beta)\ln\left(\frac{r}{a}\right) + \frac{1}{2} \frac{\eta\beta}{(1-\nu^2)} \left[\frac{b^2}{a^2} - \frac{b^2}{r^2} \right] E\phi \quad (28)$$

$$\sigma_\theta = \sigma_r + \sigma_0(1+\eta\bar{\epsilon}^P) \quad (29)$$

where σ_0 , η , $\bar{\epsilon}^P$ are the initial yield stress, hardening parameter, and equivalent plastic strain, respectively, and

$$\bar{\epsilon}^P = \frac{-2}{\sqrt{3}} \left[\phi b^2/r^2 - (1-\nu^2)\sigma_0/E \right] / \left[1 + \frac{2}{\sqrt{3}} (1-\nu^2)\eta\sigma_0/E \right] \quad (30)$$

$$\phi = [E\alpha_{22k} \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} - E\alpha_{12} + (1-2\nu)(1+\nu)]q/E \quad (31)$$

$$p = \sigma_0(1-\eta\beta)\ln \frac{b}{a} + q \left\{ 1 + \frac{1}{2} \eta\beta \left(\frac{b^2}{a^2} - 1 \right) [Ak \frac{(c/b)^{2k} + 1}{(c/b)^{2k} - 1} + B + 1] \right\} \quad (32)$$

It is interesting to point out that p is a linear function of q . Similarly, when evaluating u at the bore from Eq. (27), we obtain

$$u_a/a = -(1-2\nu)(1+\nu)P/E + \phi b^2/a^2 \quad (33)$$

which can also be expressed as a linear function of q with the aid of Eqs. (31) and (32). Since the relation between q and u_b is linear from Eq. (11), p and u_a , given by Eqs. (32) and (33), respectively, can be expressed as linear functions of u_b .

FAILURE ANALYSIS

Since the steel liner is ductile and failure precedes by plastic flows, a nonlinear stress analysis beyond the elastic limit is required. The liner is considered as failure when the maximum stress or maximum strain reaches the ultimate limit (σ_u or ϵ_u). The steel is assumed to be elastic-plastic, linear strain-hardening with $\sigma_0 = 120$ Ksi, $E_t = 120$ Ksi (826.8 Mpa), and σ_u (ultimate strength) = 140 Ksi (964.6 Mpa). The composite jacket is elastically-orthotropic, and brittle failure is considered with the maximum strain criterion (ref 5). The maximum strain from each simple test is either measured or computed from the measured strength divided by the elastic modulus. For the composite jacket used here, the maximum strain criterion is

$$-\epsilon_x'^* \leq \epsilon_\theta \leq \epsilon_x^* \quad \text{and} \quad -\epsilon_y'^* \leq \epsilon_r \leq \epsilon_y^* \quad (34)$$

where

$$\epsilon_x^* = X/E_\theta, \quad \epsilon_x'^* = X'/E_\theta, \quad \epsilon_y^* = Y/E_r, \quad \epsilon_y'^* = Y'/E_r \quad (35)$$

and $X, X', Y, Y' = 262, 225, 8.7, 21.8$ Ksi (1805, 1550, 60, 150 Mpa), respectively.

DISCUSSION OF RESULTS

Given any value of internal pressure, we can obtain numerical results for the stresses and strains in the radial and tangential directions and also for the displacement at any radial position in a compound tube. The actual specimens were constructed (ref 1) using steel liners with two thicknesses and the

appropriate thickness of the composite circumferentially wound on the liner. The geometric dimensions (a,b,c) for the three composite tubes are (0.9, 1.0, 1.189), (0.9, 1.07, 1.189), and (0.9, 1.07, 1.391) inch. The pressure at the interface between the liner and jacket has been obtained as a function of internal pressure, and the results for three cases are shown in Figure 2. In this figure we also show the limits of internal pressure in the elastic-plastic range, i.e., $(p^*, p^{**}) = (20.48, 23.93), (23.06, 28.75), (27.47, 34.98)$ Ksi, respectively. The results of the hoop strains at the bore, the interface between the liner and jacket, and the outside surface for three cases are shown as functions of internal pressure in Figures 3, 4, and 5, respectively. The complete (including elastic, elastic-plastic, and fully-plastic) ranges of loadings up to failure have been considered. The maximum values of internal pressure that these compound tubes can contain without failure are $p_f = 50.693, 48.483, \text{ and } 69.931$ Ksi for cases 1, 2, and 3, respectively, and the corresponding hoop strain is 1.12 percent. The results of hoop stresses at the bore ($\sigma_{\theta/a}$) and at the interface (σ_{θ/b_-} and σ_{θ/b_+}) are shown as functions of internal pressure in Figures 6, 7, and 8 for three cases. It should be noted that the hoop stresses at the interface are discontinuous with b_- and b_+ representing the location in the liner and jacket, respectively. These figures show very clearly that the results change drastically when yielding occurs. The relation changes from linear to nonlinear when yielding sets in, and a more significant change occurs when the fully-plastic state is reached. The distributions of hoop stresses in the liner and jacket can be obtained at any given value of internal pressure. In Figures 9, 10, and 11, for cases 1, 2, and 3, respectively, we present the stress distributions for five values of internal pressure. The first three values correspond to initial yielding, 50 percent yielding, and 100 percent yielding. The percent yielding in the elastic-plastic range is defined

by $(p-a)/(b-a) \times 100$ percent. After the fully-plastic state is reached, the stress distribution changes drastically as shown in the figures for the last three values of internal pressure. The hoop stresses in the liner decrease slightly, but those in the jacket increase elastically as internal pressure is increased.

CONCLUSION

The stresses, strains, and displacements in the liner and jacket can be obtained analytically for all loading ranges up to failure. The plastic deformation in the liner has a significant effect on the overall performance of the composite structure.

REFERENCES

1. Withereff, M. D. and Scavullo, M. A., "Stress Analysis and Weight Savings of Internally Pressurized Composite-Jacketed Isotropic Cylinders," J. Pressure Vessel Tech., Vol. 112, November 1990, pp. 397-403.
2. Bland, D. R., "Elastoplastic Thick-Walled Tubes of Work-Hardening Material Subject to Internal and External Pressures and to Temperature Gradients," J. Mech. Phys. Solids, Vol. 4, 1956, pp. 209-229.
3. Chen, P. C. T., "Stress and Deformation Analysis of Autofrettaged High Pressure Vessels," ASME Pressure Vessels and Piping, Vol. 110, July 1986, pp. 61-67.
4. Chen, P. C. T., "Elastic-Plastic Analysis of a Thick-Walled Composite Tube Subjected to Internal Pressure," ARDEC Technical Report ARCCB-TR-89027, Benet Laboratories, Watervliet, NY, October 1989.
5. Tsai, S. W., Composite Design, 3rd Edition, Think Composites, Dayton, Ohio, 1987.

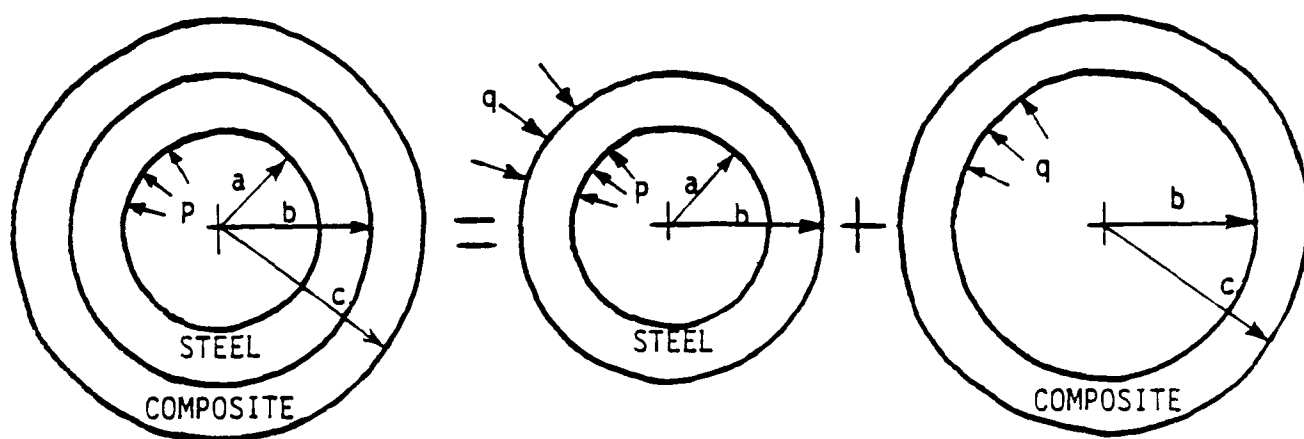


Figure 1. Schematic of a compound tube problem.

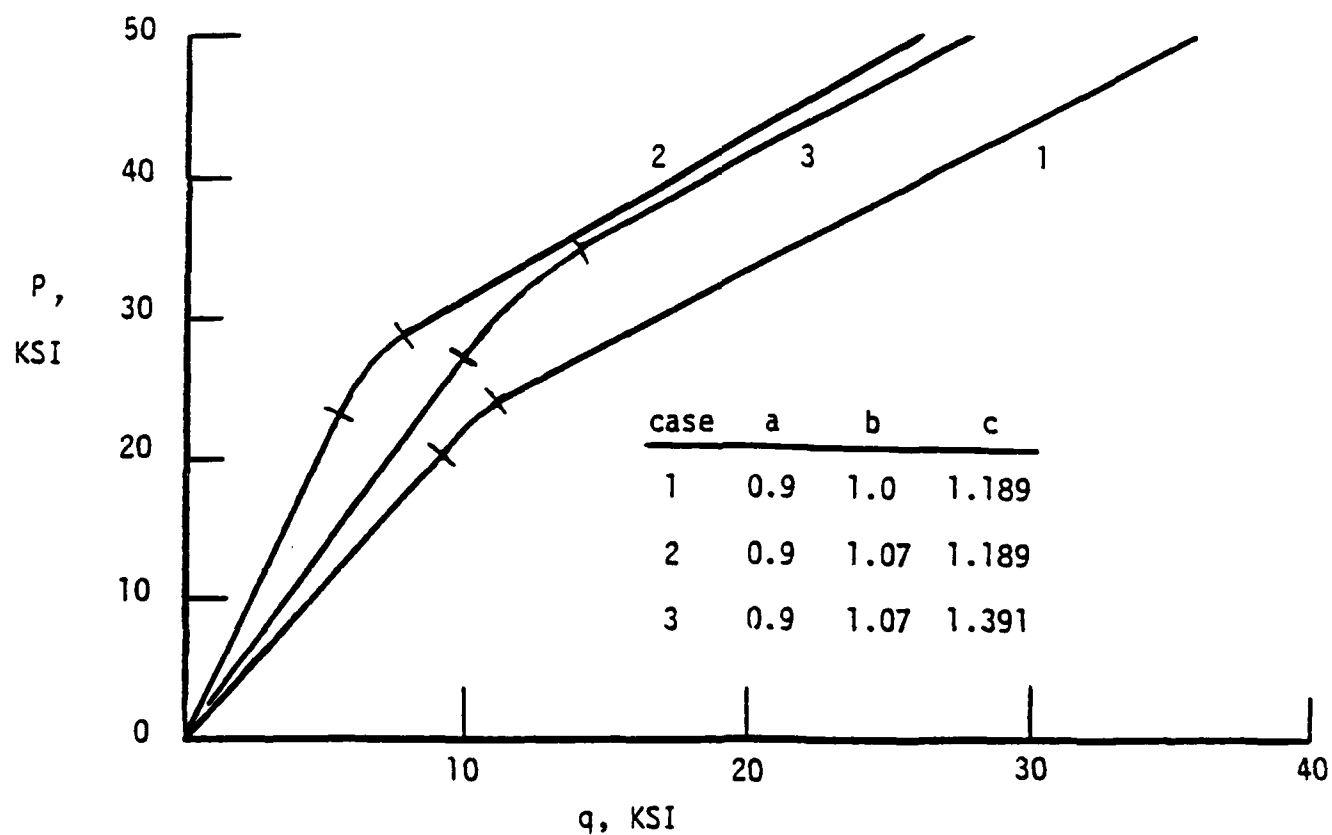


Figure 2. Interface pressure as a function of internal pressure.

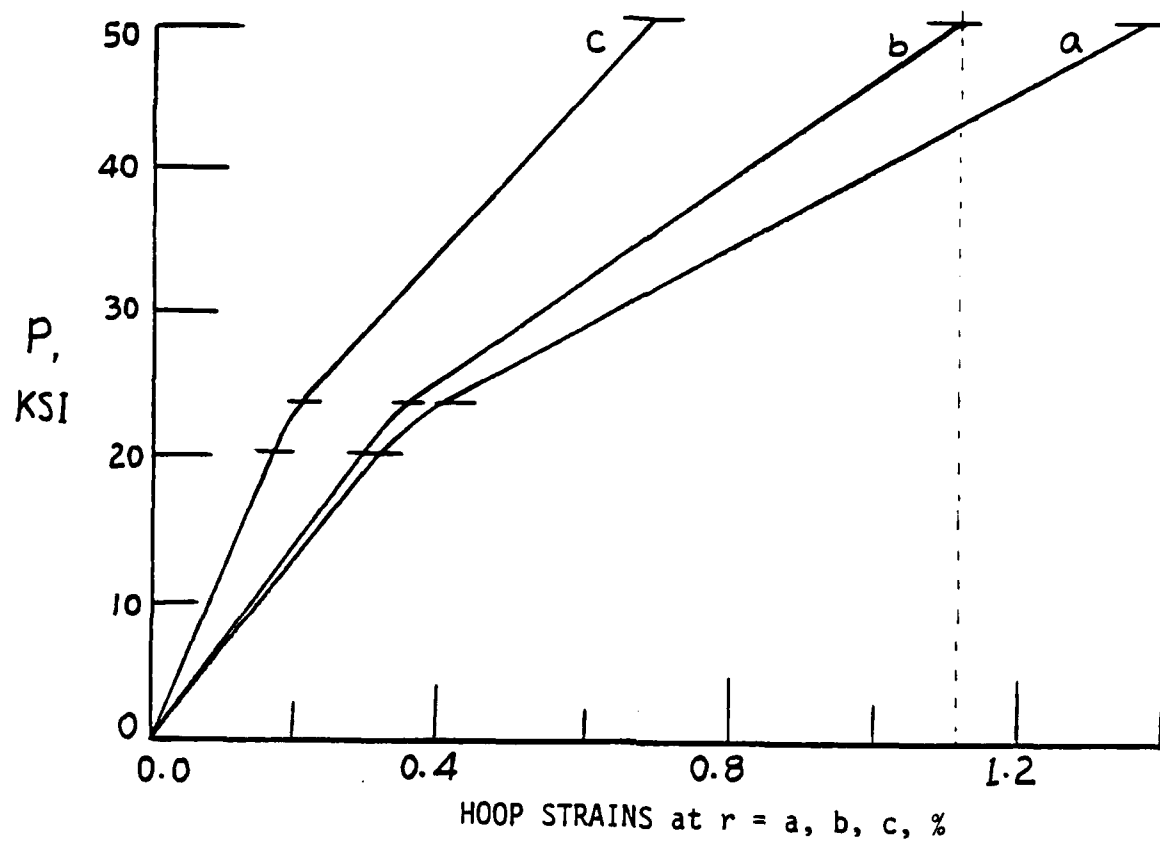


Figure 3. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 1.

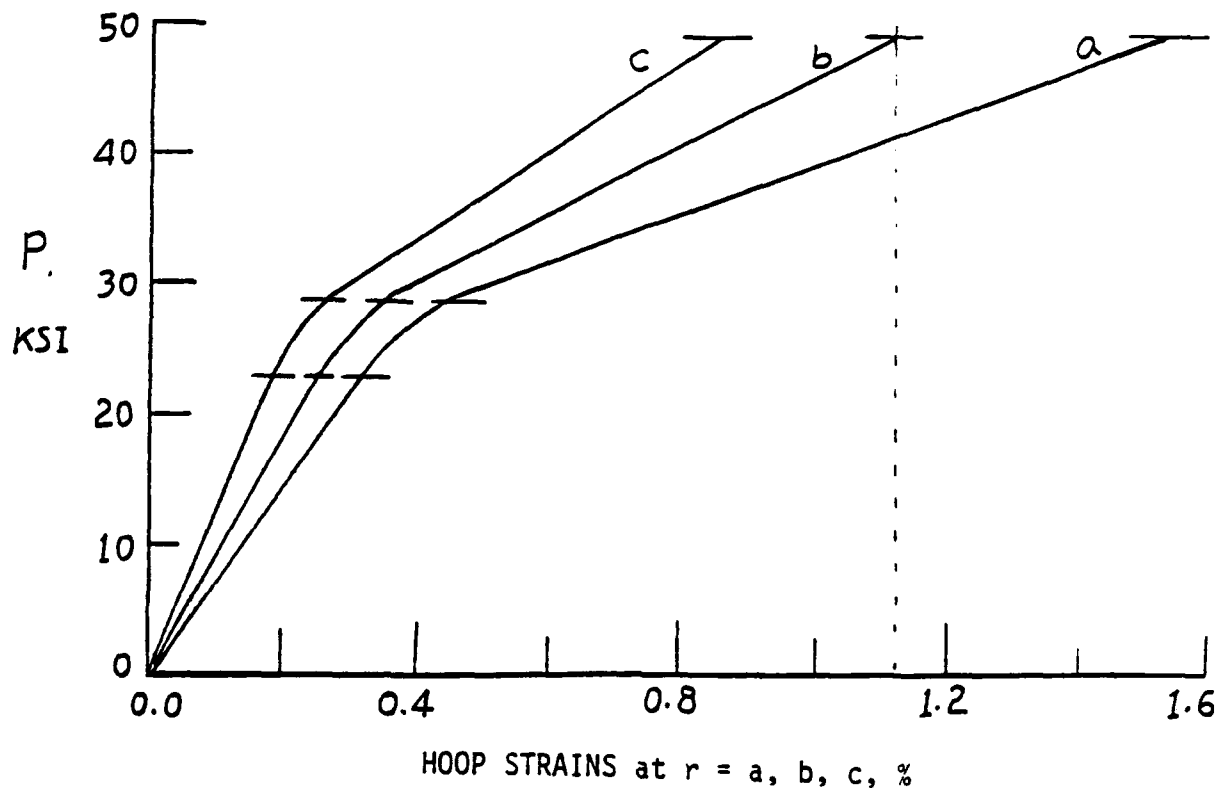


Figure 4. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 2.

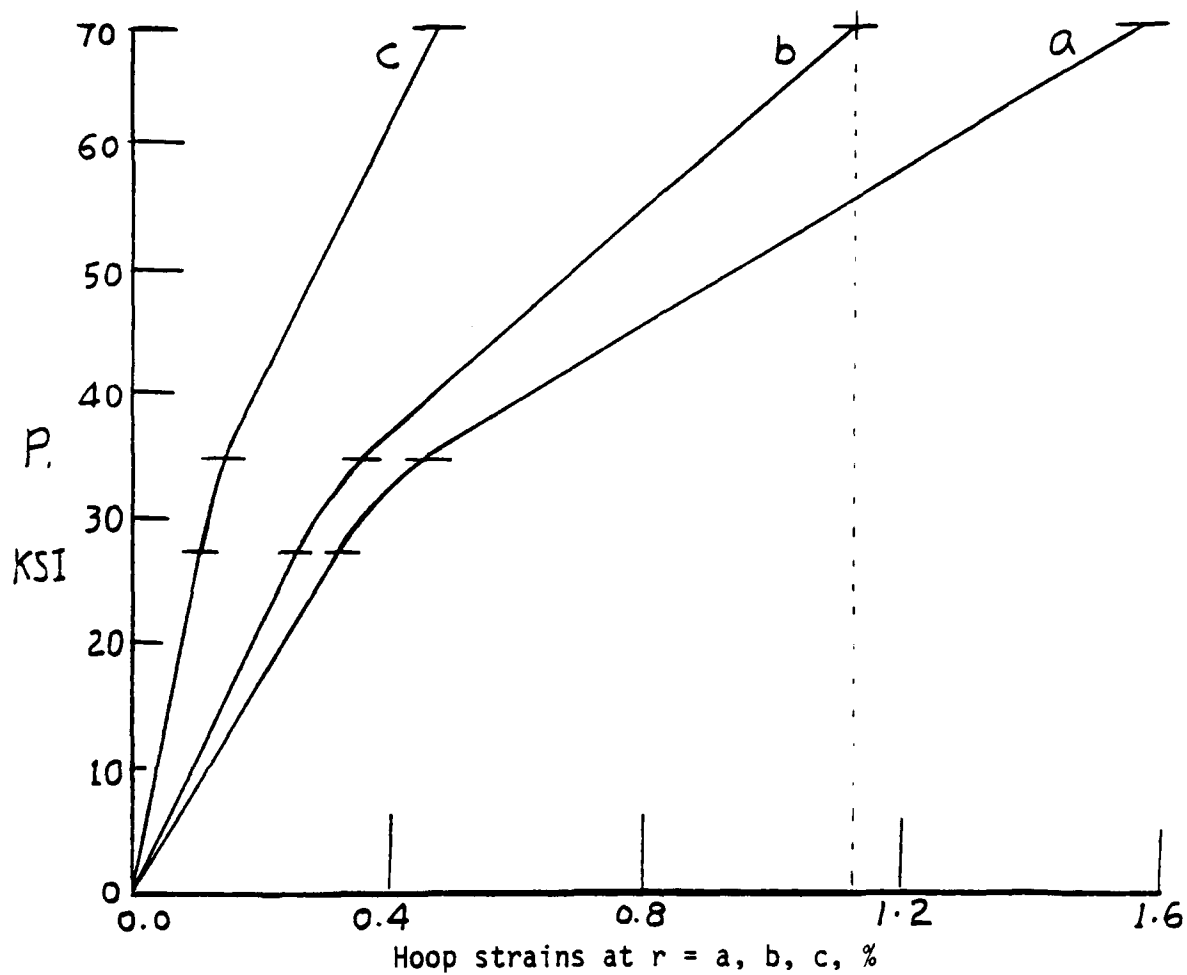


Figure 5. Hoop strains at the bore, interface, and outside surface as functions of internal pressure for case 3.

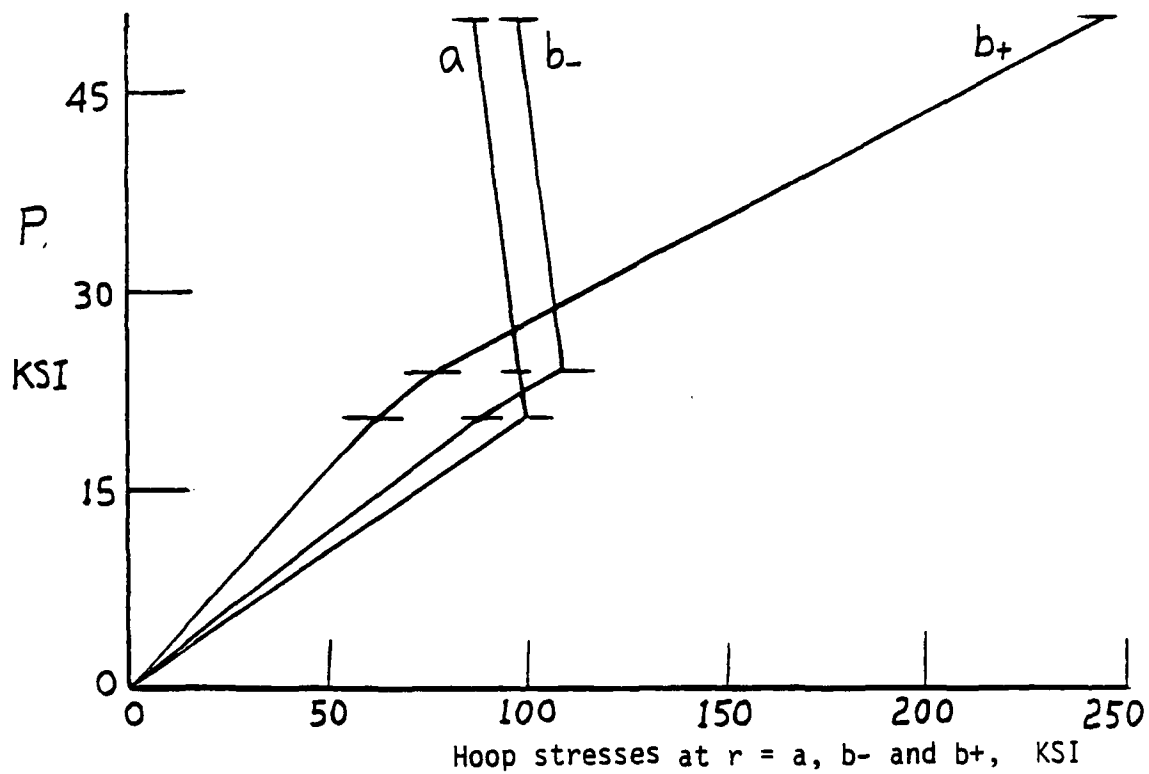


Figure 6. Hoop stresses at the bore and interface as functions of internal pressure for case 1.

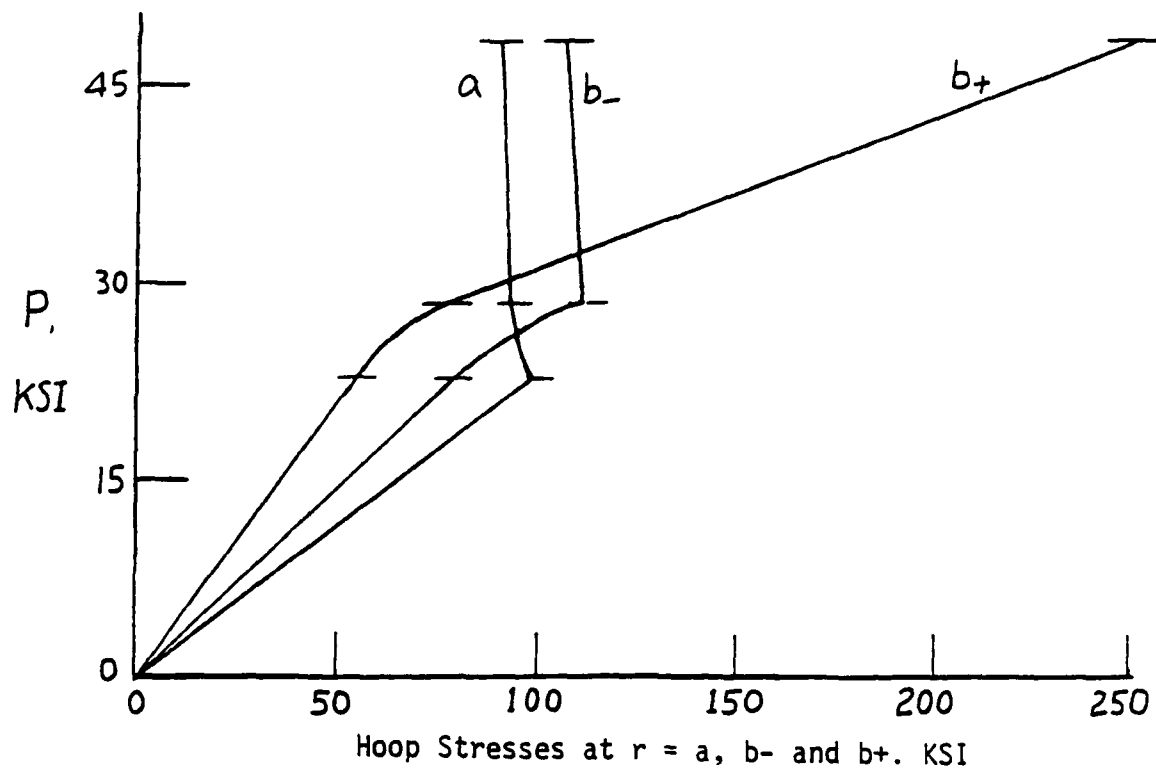


Figure 7. Hoop stresses at the bore and interface as functions of internal pressure for case 2.

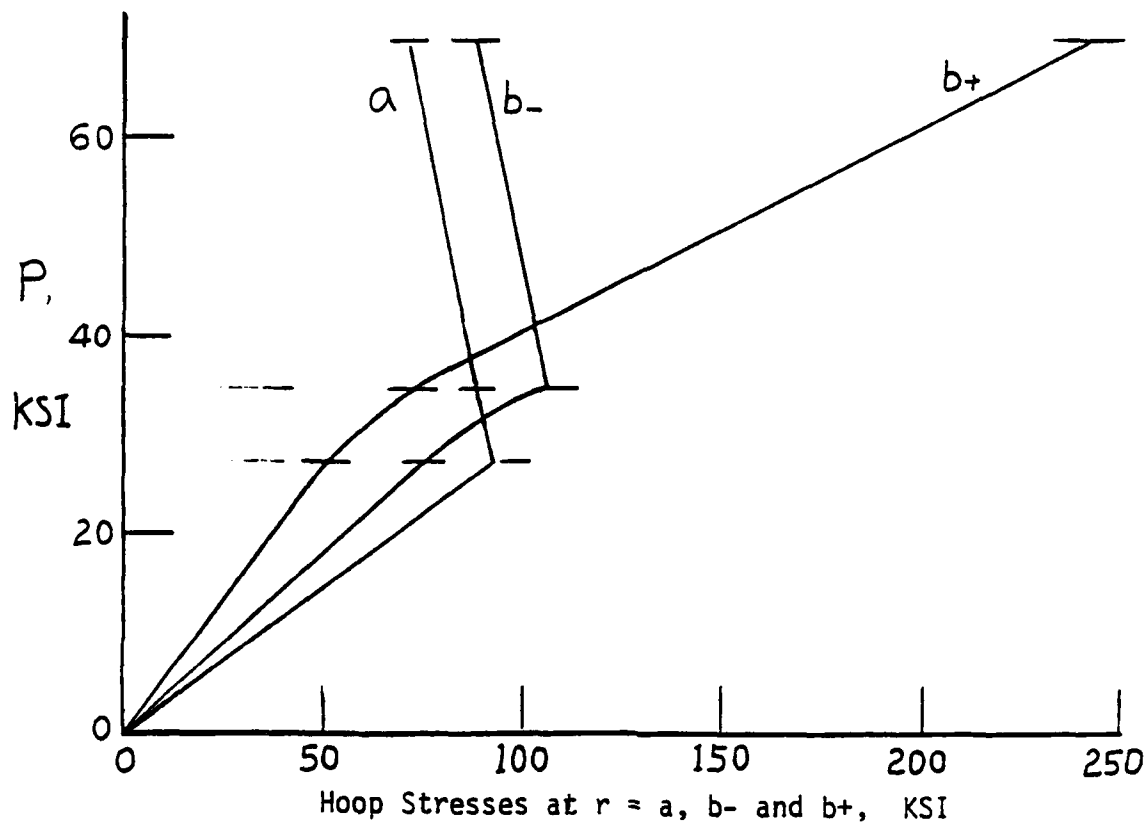


Figure 8. Hoop stresses at the bore and interface as functions of internal pressure for case 3.

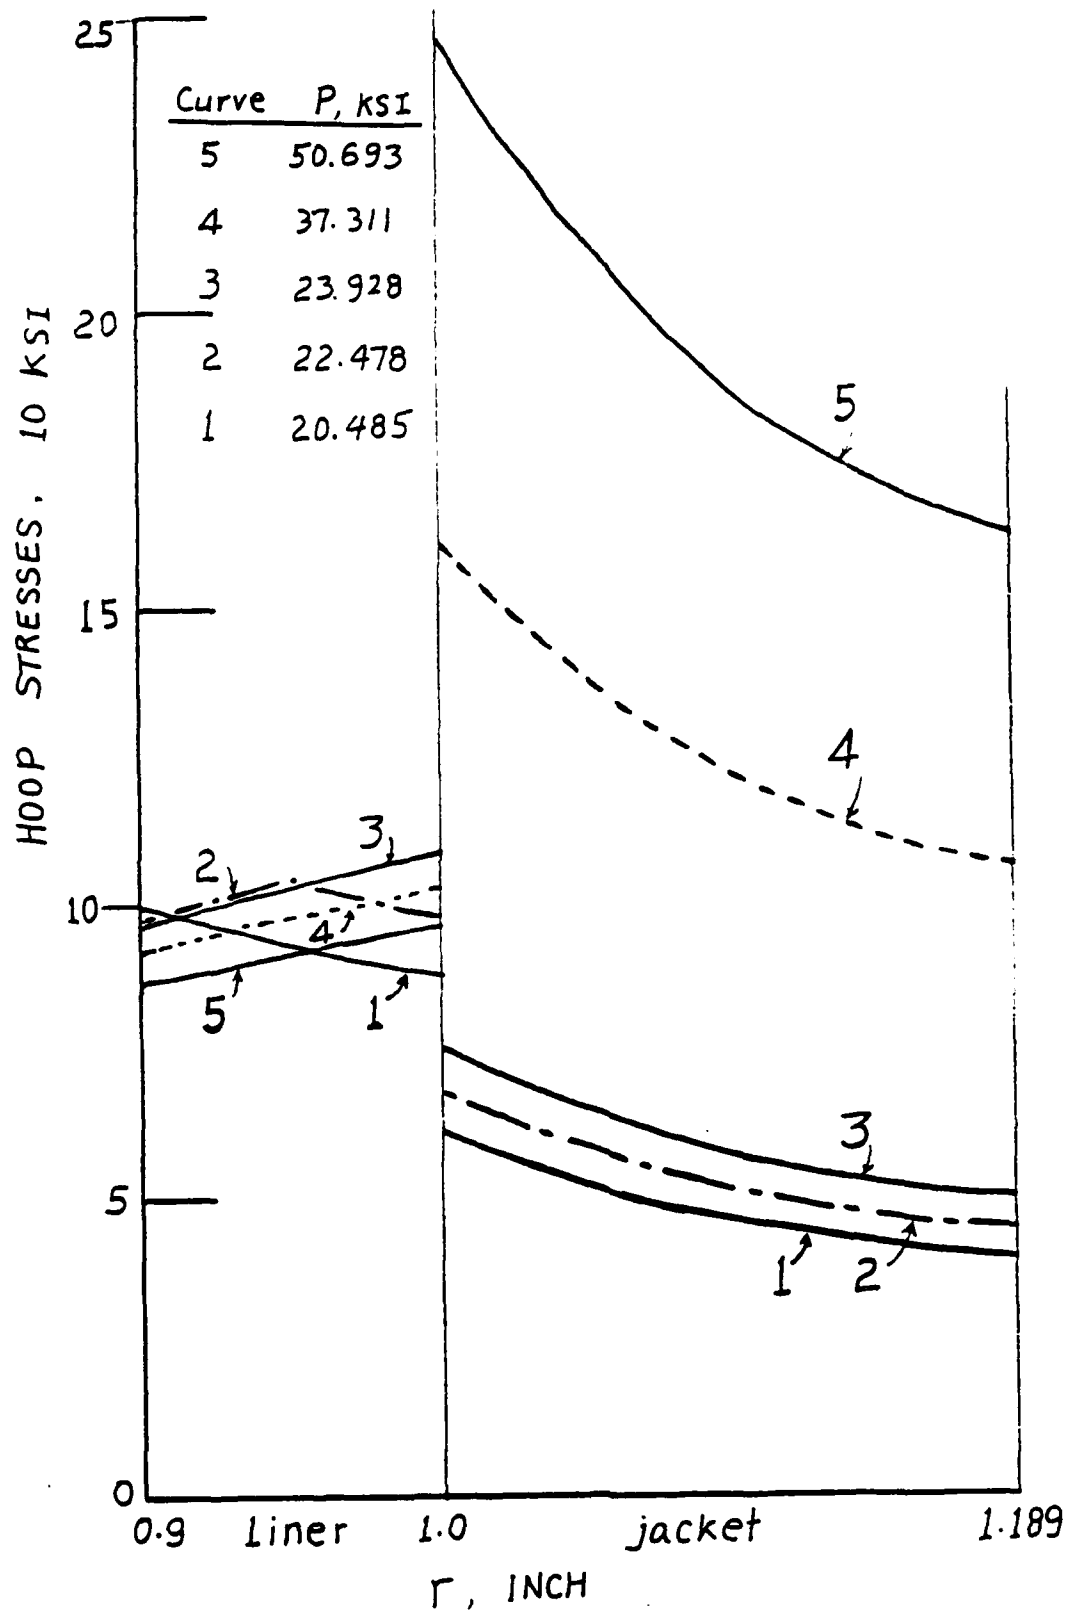


Figure 9. Distribution of hoop stresses in the liner and jacket for case 1.

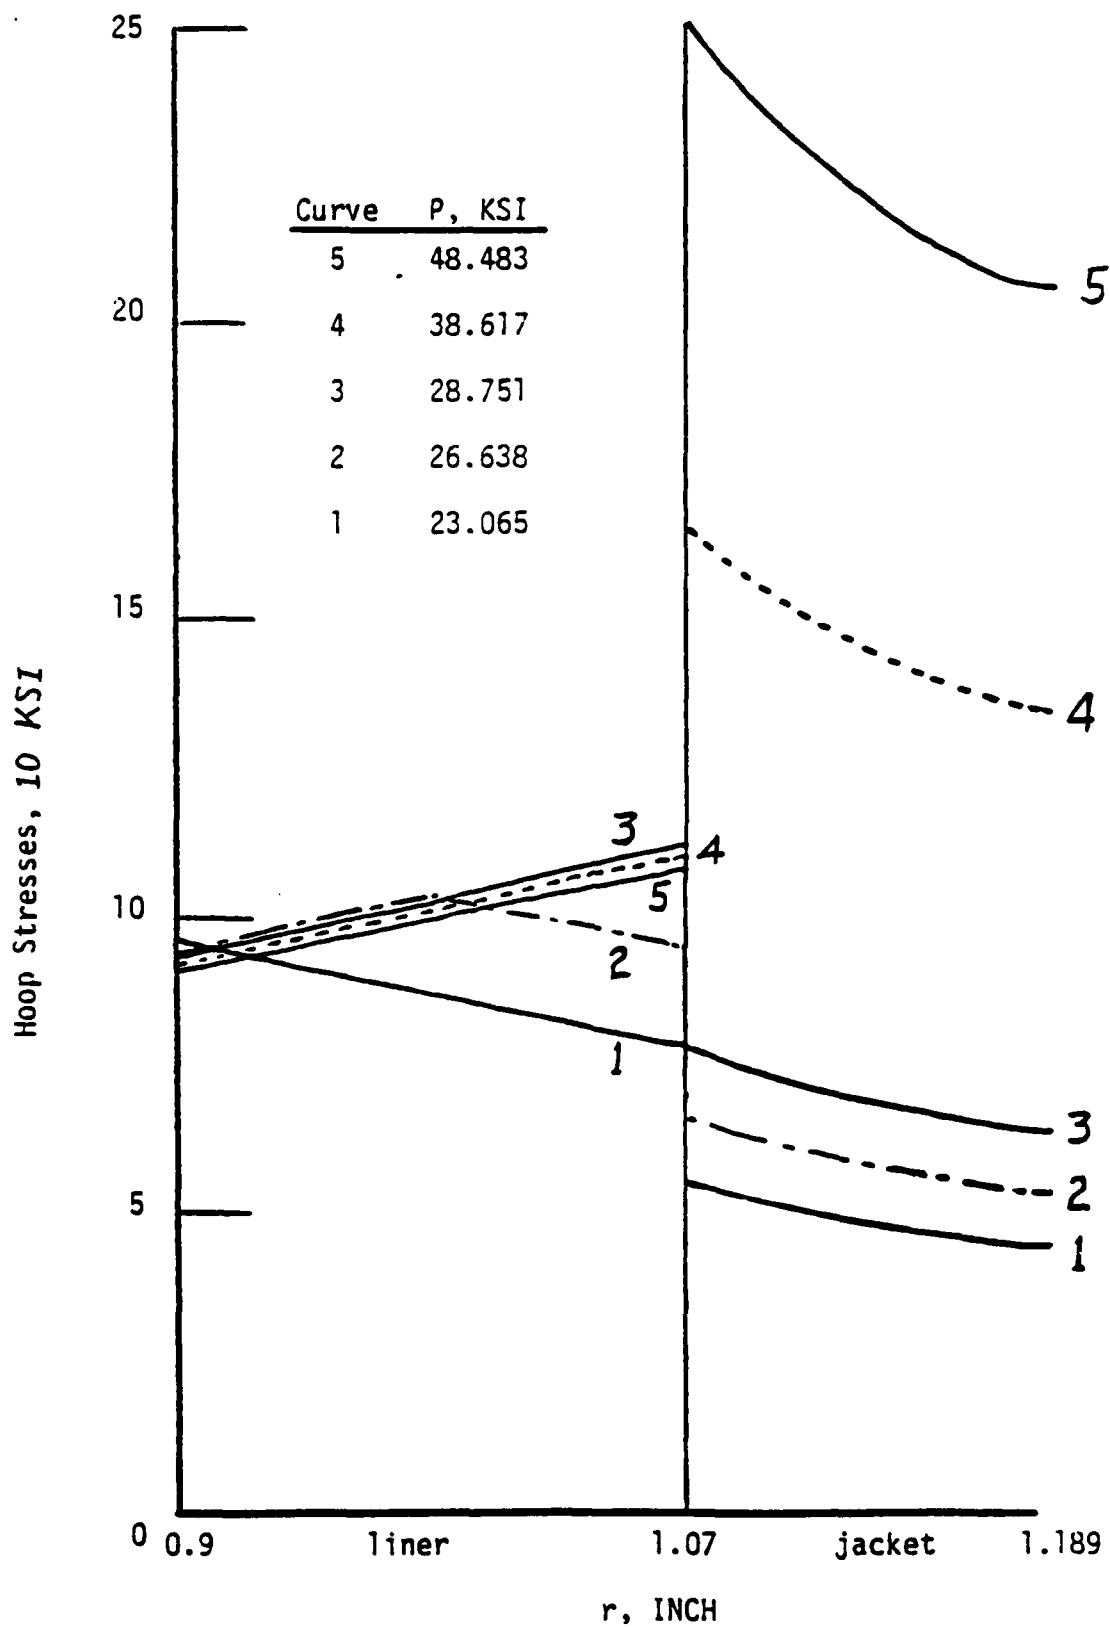


Figure 10. Distribution of hoop stresses in the liner and jacket for case 2.

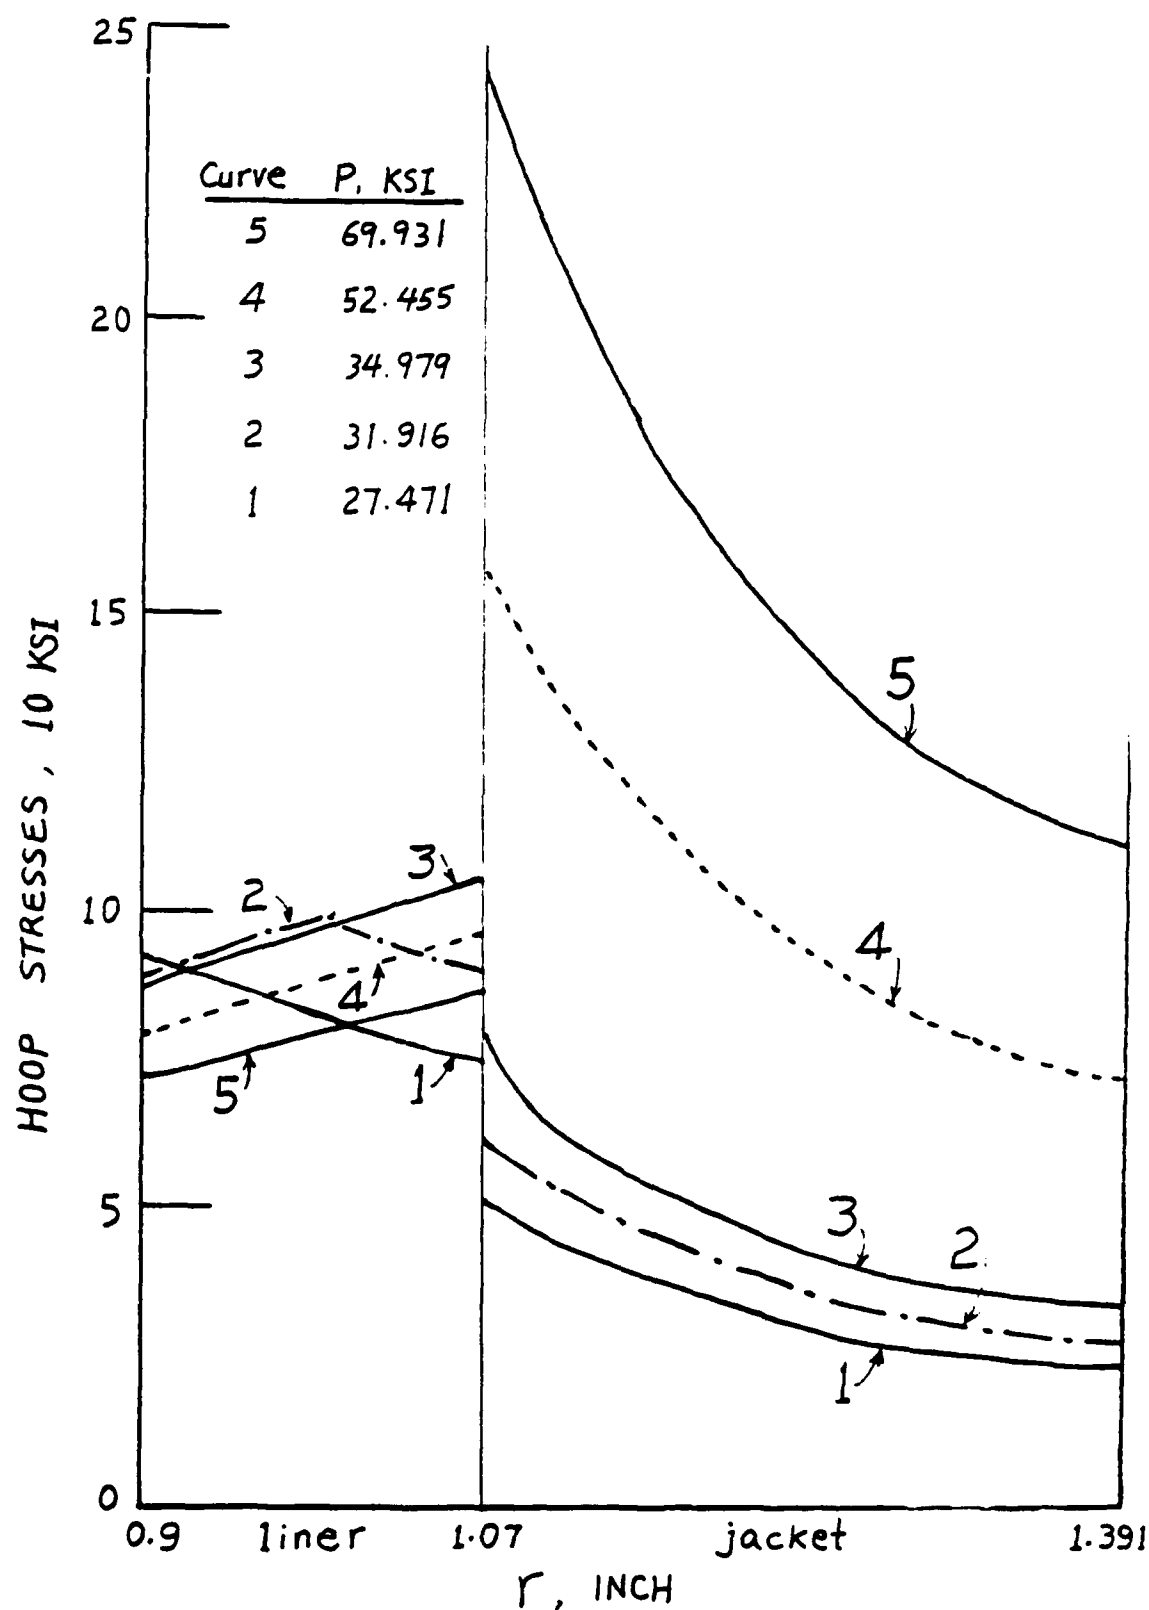


Figure 11. Distribution of hoop stresses in the liner and jacket for case 3.

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

NO. OF COPIES

CHIEF, DEVELOPMENT ENGINEERING DIVISION

ATTN: SMCAR-CCB-DA

-DC

-DI

-DR

-DS (SYSTEMS)

1
1
1
1
1

CHIEF, ENGINEERING SUPPORT DIVISION

ATTN: SMCAR-CCB-S

-SD

-SE

1
1
1

CHIEF, RESEARCH DIVISION

ATTN: SMCAR-CCB-R

-RA

-RE

-RM

-RP

-RT

2
1
1
1
1
1

TECHNICAL LIBRARY

ATTN: SMCAR-CCB-TL

5

TECHNICAL PUBLICATIONS & EDITING SECTION

ATTN: SMCAR-CCB-TL

3

OPERATIONS DIRECTORATE

ATTN: SMCWV-ODP-P

1

DIRECTOR, PROCUREMENT DIRECTORATE

ATTN: SMCWV-PP

1

DIRECTOR, PRODUCT ASSURANCE DIRECTORATE

ATTN: SMCWV-QA

1

NOTE: PLEASE NOTIFY DIRECTOR, BENET LABORATORIES, ATTN: SMCAR-CCB-TL, OF ANY ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
ASST SEC OF THE ARMY RESEARCH AND DEVELOPMENT ATTN: DEPT FOR SCI AND TECH THE PENTAGON WASHINGTON, D.C. 20310-0103	1	COMMANDER ROCK ISLAND ARSENAL ATTN: SMCRI-ENM ROCK ISLAND, IL 61299-5000	1
ADMINISTRATOR DEFENSE TECHNICAL INFO CENTER ATTN: DTIC-FDAC CAMERON STATION ALEXANDRIA, VA 22304-6145	12	DIRECTOR US ARMY INDUSTRIAL BASE ENGR ACTV ATTN: AMXIB-P ROCK ISLAND, IL 61299-7260	1
COMMANDER US ARMY ARDEC ATTN: SMCAR-AEE	1	COMMANDER US ARMY TANK-AUTMV R&D COMMAND ATTN: AMSTA-DDL (TECH LIB) WARREN, MI 48397-5000	1
SMCAR-AES, BLDG. 321	1	COMMANDER	
SMCAR-AET-O, BLDG. 351N	1	US MILITARY ACADEMY	1
SMCAR-CC	1	ATTN: DEPARTMENT OF MECHANICS	
SMCAR-CCP-A	1	WEST POINT, NY 10996-1792	
SMCAR-FSA	1		
SMCAR-FSM-E	1	US ARMY MISSILE COMMAND	
SMCAR-FSS-D, BLDG. 94	1	REDSTONE SCIENTIFIC INFO CTR	2
SMCAR-IMI-I (STINFO) BLDG. 59	2	ATTN: DOCUMENTS SECT, BLDG. 4484	
PICATINNY ARSENAL, NJ 07806-5000		REDSTONE ARSENAL, AL 35898-5241	
DIRECTOR US ARMY BALLISTIC RESEARCH LABORATORY ATTN: SLCBR-DD-T, BLDG. 305	1	COMMANDER US ARMY FGN SCIENCE AND TECH CTR ATTN: DRXST-SD	1
ABERDEEN PROVING GROUND, MD 21005-5066		220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	
DIRECTOR US ARMY MATERIEL SYSTEMS ANALYSIS ACTV ATTN: AMXSY-MP	1	COMMANDER US ARMY LABCOM	
ABERDEEN PROVING GROUND, MD 21005-5071		MATERIALS TECHNOLOGY LAB	
		ATTN: SLCMT-IML (TECH LIB)	2
COMMANDER HQ, AMCCOM ATTN: AMSMC-IMP-L	1	WATERTOWN, MA 02172-0001	
ROCK ISLAND, IL 61299-6000			

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER, US ARMY AMCCOM, ATTN: BENET LABORATORIES, SMCAR-CCB-TL, WATERVLIET, NY 12189-4050, OF ANY ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST (CONT'D)

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
COMMANDER US ARMY LABCOM, ISA ATTN: SLCIS-IM-TL 2800 POWDER MILL ROAD ADELPHI, MD 20783-1145	1	COMMANDER AIR FORCE ARMAMENT LABORATORY ATTN: AFATL/MN EGLIN AFB, FL 32542-5434	1
COMMANDER US ARMY RESEARCH OFFICE ATTN: CHIEF, IPO P.O. BOX 12211 RESEARCH TRIANGLE PARK, NC 27709-2211	1	COMMANDER AIR FORCE ARMAMENT LABORATORY ATTN: AFATL/MNF EGLIN AFB, FL 32542-5434	1
DIRECTOR US NAVAL RESEARCH LAB ATTN: MATERIALS SCI & TECH DIVISION CODE 26-27 (DOC LIB) WASHINGTON, D.C. 20375	1 1	MIAC/CINDAS PURDUE UNIVERSITY 2595 YEAGER ROAD WEST LAFAYETTE, IN 47905	1
DIRECTOR US ARMY BALLISTIC RESEARCH LABORATORY ATTN: SLCBR-IB-M (DR. BRUCE BURNS) ABERDEEN PROVING GROUND, MD 21005-5066	1		

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER, US ARMY AMCCOM, ATTN: BENET LABORATORIES, SMCAR-CCB-TL, WATERVLIET, NY 12189-4050, OF ANY ADDRESS CHANGES.

DEPARTMENT OF THE ARMY

ARMAMENT RESEARCH, DEVELOPMENT AND ENGINEERING CENTER

BENÉ T LABORATORIES, CCAC

US ARMY ARMAMENT, MUNITIONS AND CHEMICAL COMMAND

WATERVLIET, N.Y. 12189-4050

OFFICIAL BUSINESS

SMCAR-CCB-TL

DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

PENALTY FOR PRIVATE USE: \$300

ADMINISTRATOR
DEFENSE TECHNICAL INFO CENTER
ATTN: DTIC-FDAC
CAMERON STATION
ALEXANDRIA, VA 22304-6145

DA Label 18-1, Sep 83
Edition of Oct 74 will be used until exhausted.